




## RDT Chamber Test.

Tested at Saint Gobain Pipelines plc, PDD, Ilkeston on 30/4/02.  
 Chamber sections are Hot pressed SMC. 150mm deep, bolted together in corners.

Unit tested H9320 - Inter-ax D400 600x600x100mm. Pad 300dia.

Test configuration as below.

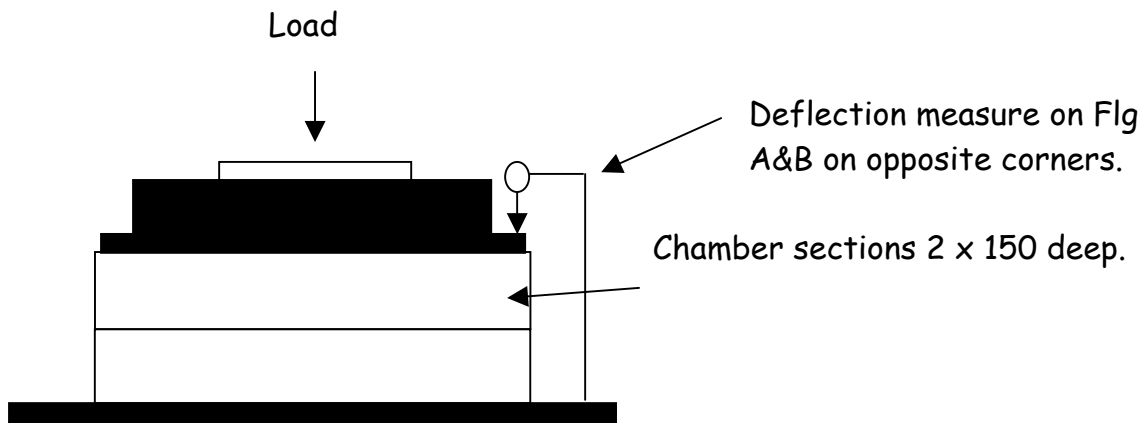

Load applied by hydraulic ram.

<u>Load KN</u>	<u>Deflection A mm</u>	<u>Deflection B mm</u>
0	0	0
100	2.56	4.45
154	4.30	5.03
200	4.80	5.41
266	5.23	5.77
302	5.38	5.92
348	5.48	5.97
404	5.58	5.84
432	5.59	5.69
0	0.96	1.22